

UNCLASSIFIED

AD NUMBER

AD820818

LIMITATION CHANGES

TO:

Approved for public release; distribution is unlimited.

FROM:

Distribution authorized to U.S. Gov't. agencies and their contractors; Critical Technology; SEP 1967. Other requests shall be referred to Air Force Rocket Propulsion Laboratory, Edward , CA. This document contains export-controlled technical data.

AUTHORITY

AFRPL ltr, 27 Oct 1971

THIS PAGE IS UNCLASSIFIED

AFRPL-TR-67-254

AD829818

DOUBLE-BASE BINDER IMPROVEMENT

DR. W. E. BAUMGARTNER
DR. G. E. MYERS, et al

LOCKHEED PROPULSION COMPANY
A DIVISION OF LOCKHEED AIRCRAFT CORPORATION
REDLANDS, CALIFORNIA

TECHNICAL REPORT AFRPL-TR-67-254

SEPTEMBER 1967

DDC
RECEIVED
OCT 10 1967
A

STATEMENT #2 UNCLASSIFIED

This document is subject to special export controls and each transmittal to foreign governments or foreign nationals may be made only with prior approval of *ADW: (RPPR-ST/WFO)*

AIR FORCE ROCKET PROPULSION LABORATORY
RESEARCH AND TECHNOLOGY DIVISION
AIR FORCE SYSTEMS COMMAND
UNITED STATES AIR FORCE
EDWARDS, CALIFORNIA

DOUBLE-BASE BINDER IMPROVEMENT

**Dr. W. E. Baumgartner
Dr. G. E. Myers, et al
Lockheed Propulsion Company**

**LOCKHEED PROPULSION COMPANY
A Division of Lockheed Aircraft Corporation
P.O. Box 111
Redlands, California 92374**

FOREWORD

This is the second Quarterly Report issued under Contract No. F04611-67-C-0078, "Double-Base Binder Improvement," covering the period 1 June through 31 August 1967 and submitted September 1967. This contract is assigned to Lockheed Propulsion Company, Redlands, California, and is monitored by Lt. William Anders, Air Force Rocket Propulsion Laboratory, Edwards, California.

Technical effort under this contract has been performed by the following: Dr. W. E. Baumgartner, (Program Manager); Dr. G. E. Myers, (principal technical investigator); E. E. Larkin, and Waldemar Koehler.

This report is unclassified in its entirety.

Publication of this report does not constitute Air Force approval of the report's findings and conclusions. It is published only for the exchange and stimulation of ideas.

William Ebelke
Colonel, USAF
Chief, Propellant Division

ABSTRACT

An investigation is underway into the physico-chemical factors controlling the mechanical behavior of slurry cast and base grain composite double-base propellants, the primary objective being to improve the mechanical properties of slurry cast systems at least up to those of analogous base grain systems. Studies during the second quarter involved establishment and testing of tritium autoradiographic procedures for investigating inhomogeneities in these systems; synthesis of tritiated ingredients; preparation of casting powder and base grain propellant by NOS and of special ball powders by Olin; observations of glass transitions in NC gels and plasticizers; construction of microscope-strain apparatus.

(The reverse is blank)

TABLE OF CONTENTS

<u>Section</u>		<u>Page</u>
I	INTRODUCTION AND SUMMARY	1
II	DISCUSSION	3
1.	BINDER PROPELLANT INHOMOGENEITIES	3
a.	Autoradiographic Experiments	3
b.	Synthesis of Tritium-Labeled Ingredients	4
2.	MECHANICAL BEHAVIOR	7
a.	Propellant for Macroscopic Studies	7
b.	Low Temperature Transitions	8
c.	Microscope-Strain Apparatus	8
3.	FUTURE WORK	13

(The reverse is blank)

SECTION I

INTRODUCTION AND SUMMARY

In this program, an investigation is being conducted into physico-chemical factors controlling the mechanical behavior of slurry cast and base grain composite double-base propellants (CMDB), the primary objective being to improve the mechanical behavior of slurry cast systems to the point where they at least equal those of similar base grain propellants.

The base grain process has been used almost exclusively whenever nitroglycerin serves as a plasticizer and generally (though not always) produces propellants of superior mechanical properties relative to those from the slurry cast process. The latter process, however, possesses very distinct processing advantages over the base grain because of its comparative simplicity, safety, and versatility.

While extensive investigations have been made into the general problem of CMDB propellant mechanical behavior, our understanding still remains comparatively poor, in both a fundamental and an applied sense. Considering their wide usage, in fact, nitrocellulose (NC) gels are perhaps the least understood of the major thermoplastic systems. Nevertheless, the CMDB propellants, and particularly those prepared by the slurry cast process, appear at present to offer the greatest potential as a vehicle for high energy ingredients. Thus, a significant improvement in slurry cast propellant mechanical behavior is much to be desired.

Because of the complexity of the CMDB system, any program expecting to achieve significant improvements in mechanical behavior within a reasonable period must be highly selective in its choice of variables for study and in the depth to which it can delve among those variables. In the present program, specific tasks have been selected, each dealing with a critical facet of the overall program. Under each task, the particular phenomena which are believed to be controlling will be singled out for thorough study.

The major program tasks are concerned with:

- Detection of various types of binder micro-inhomogeneity, determination of consequent limitations upon physical properties, and study of means to overcome such deficiencies.
- Differentiation among the various factors controlling the separate processes occurring during combined NC solution/gelation/cross-linking to provide the basis for development of an optimized binder system.
- Establishment of the inherent binder-solids adhesional character in the optimized binder system and determination of means to overcome deficiencies to yield an optimized propellant.

Efforts during this quarter included:

- **Establishment of tritium autoradiographic procedures and conduct of preliminary experiments for the purpose of determining binder/propellant inhomogeneities.**
- **Synthesis of tritium-labeled double-base ingredients--EGDN, TMETN, NC.**
- **Preparation of casting powder and base grain propellant at the Naval Ordnance Station to be employed in a comparison of mechanical behavior of base grain and slurry cast propellants at LPC. Procurement of special ball powder samples from Olin.**
- **Initiation of studies of low temperature transitions in CMDB binders/propellants.**
- **Design and construction of an apparatus permitting microscopic observation of thin specimens during straining.**

SECTION II

DISCUSSION

1. BINDER - PROPELLANT INHOMOGENEITIES

Past investigations have demonstrated the existence of relatively gross inhomogeneities in some CMDB binders and propellants. Definitive studies are lacking, however, with regard to the existence of more subtle inhomogeneities, the extent of their influence upon mechanical behavior, and their dependence upon ingredient structure and form. This program is attempting to resolve these questions with the use of tritium autoradiography, which is capable of greater specificity, spatial resolution, and sensitivity than can be obtained by applying more conventional techniques to such systems (e.g. x-ray radiography, electron or optical microscopy). The weak β -rays of tritium, for example, in principle permit localizations of labeled ingredients to be determined within a resolution of one micron.

a. Autoradiographic Experiments

Autoradiographic procedures involve the following general steps:

- (1) Sample preparation, including introduction of tritium-labeled ingredients.
- (2) Preparation of thin sections of the system of interest.
- (3) Application of radiation-sensitive photographic emulsions or films.
- (4) Storage/exposure of composite sample, followed by development and microscopic examination.

These steps and efforts taken to date to implement them are discussed in greater detail in the following:

- Sample preparation: This necessitates first the synthesis of labeled materials, e.g., tritiated plasticizers, NC, crosslinkers, and efforts in this direction are discussed in detail in Section 1b below. Incorporation of the tritiated ingredients into binder/propellants is straightforward. We have constructed equipment for use in making the necessary 5 to 10 g mixes under vacuum and with careful temperature controls.
- Preparation of thin sections: Microscopic examination of the final autoradiograph requires the use of relatively flat and transparent sections of the system of interest. Thus far these specimens have been prepared by sandwiching a small amount (~10 mg) of the uncured mix between two microscope slides. After cure the cover slide is removed, leaving an approximately 0.010 inch thick

section. Ultimately the more desirable procedure will be to microtome sections from bulk (5 to 10 g) samples and cement these to a microscope slide; brief experiments have demonstrated the feasibility of this operation.

- Application of radiation sensitive photographic emulsion: This coating must adhere very closely to the section because of the very short path length of tritium β rays in air. Of the applicable procedures here, experiments have demonstrated the superiority of coating with molten (40°C) NTB-2 Kodak Nuclear Track Emulsion, using a simple dipping technique. After dipping, the samples are allowed to drain and dry in the dark before storing in dry, light-tight boxes.
- Storage/exposure, etc., of emulsion-coated sample: Wherever the tritium-labeled ingredient is concentrated in the sample, the resultant β rays will cause darkening of the immediately adjacent film, and this darkening may be correlated with any optically observable structure within the sample. Since the average path length of tritium β -rays is about 1 micron in organic matter, resolution is of that order and only the topmost layer of sample actually affects the photographic emulsion.

Controversy exists as to whether the emulsion-coated sample can be stored (exposed) at ambient temperature or should be exposed at lower temperatures. Both may well prove desirable for this study but as yet only low temperature (4°C) has been employed to minimize possible chemical interactions between sample and emulsion.

Exposure time obviously depends upon tritium activity level and the extent of ingredient localization, i. e., upon microactivity levels. Following guidelines in the biological literature, initial experiments here were performed with PNC, TEGDN, tritiated ethylene glycol mixtures at various activity levels. These were exposed for varying times at 4°C and subsequent development and examination indicated that ten days with an overall activity of 5 $\mu\text{C/g}$ mix resulted in detectable localized darkening of the film.

After the samples are stored for a sufficient length of time, the slides were developed using standard photographic techniques. The developer is Kodak Dektol (1:1) and the sample is fixed in Kodak Acid Fixer. Development is performed with the emulsion still coating the sample so that subsequent microscopic examination of the composite will permit correlation between the radiograph and any optically observable structure.

b. Synthesis of Tritium-Labeled Ingredients


Initial materials selected here are nitrocellulose and the plasticizers EGDN and TMETN. Ultimately it is expected that other plasticizers, as well as crosslinkers and catalysts, will be prepared.

(1) EGDN

Labeled EGDN (25 g) has been prepared at sufficiently high activity (170 $\mu\text{c/g}$) by nitration of tritiated ethylene glycol. This was carried out by stepwise addition of the glycol to a two-phase mixture of $\text{HNO}_3/\text{H}_2\text{SO}_4$ and CH_2Cl_2 kept below 20°C . After two hours at ambient temperature the acid layer was drawn off and discarded and the CH_2Cl_2 layer washed with H_2O and NaHCO_3 . Subsequent drying, filtration, and vacuum removal of CH_2Cl_2 gives the EGDN in almost 100 percent yield. The purity of the high level EGDN (H^3) was verified by CH_2Cl_2 elution from an alumina column, using liquid scintillation counting of the fractions.

(2) TME TN

Three grams of high level (585 $\mu\text{c/g}$) trimethylolethane (TME) have been synthesized by a combined aldol condensation/Cannizzaro reaction between propionaldehyde and tritiated formaldehyde (Ref. 1).



The literature procedure was followed closely except that greater incorporation of tritium was found if, instead of adding the propionaldehyde slowly to the mixed cold/labeled formaldehyde, one mole of labeled formaldehyde was first reacted per mole of propionaldehyde and the remaining two moles of formaldehyde subsequently reacted. Based upon the overall theoretical yield of tritiated TME, a 33 percent yield was actually obtained. Although this high level material has not yet been nitrated, successful nitrations of cold and low level TME have been conducted using the same procedure employed for the EGDN.

(3) NC

One intent of this program is to study the differences in structure of base brain and slurry cast propellants by incorporating labeled NC into casting powder and PNC and performing autoradiographic observations upon propellants prepared from them. For this purpose the labeled NC must not differ significantly in behavior from NC normally employed in preparing casting powder and PNC.

Initial experiments have centered upon labeling NC by means of low degrees of reaction with tritiated acetic anhydride. Since the latter is available at quite high activities, it should be possible to prepare sufficiently active NC without reacting more than 1 to 2 percent of the NC residual hydroxyls. This should constitute negligible modification of the NC structure and properties as long as the acetylation conditions were mild enough to preclude other structural changes, e.g., oxidation, denitration.

Successful incorporation of tritiated acetic anhydride has been accomplished in preliminary experiments under heterogeneous (Ref. 2) and homogeneous conditions using fibrous NC (12.6 percent N). Results of one series of experiments in the heterogeneous system are shown in Table I.

TABLE I
HETEROGENEOUS ACETYLATION OF NC

Reaction System	Volume of Added Acetic Anhydride (a)	Total Activity in Reaction Mixture	Tritium Activity in Product	% of Added Activity Incorporated	% Residual Hydroxyls Acetylated (b)
2.5 g NC; 60 ml CH ₂ Cl ₂ ; 100 μ l 70% HClO ₄	250 μ l	117 μ curie	1.3 μ c/g	3.6%	2%
	500 "	234 "	10.0 "	10.7%	12%
Variable acetic anhydride; Reflux 2 hours.	750 "	351 "	23 "	16.4%	26%

(a) 0.47 μ c/ μ l.

(b) Based upon % activity incorporated

Because of competition for the anhydride between the NC hydroxyls and the water present from the NC and HClO_4 , the percent acetylation is not a linear function of the added amount of anhydride. Nevertheless, it is obvious that a labeled NC of quite small degrees of acetylation can be prepared with this procedure by proper control of water/anhydride/NC ratios and of anhydride specific activity.

The heterogeneous systems suffer from one drawback, however, namely the probability that the acetate groups are not uniformly attached but are concentrated upon NC molecules in the outer or amorphous regions of the fibers. Experiments have therefore been extended to homogeneous systems, i. e., those in which the NC is dissolved. Acetone was first employed as solvent but this system produced negligible reaction with the NC at varying (but low) levels of acetic anhydride and HClO_4 , ambient or reflux temperatures, anhydrous or containing moisture from the NC and 70 percent HClO_4 .

With the thought that this absence of NC reaction might be the consequence of competition with the enol form of acetone, NC solvents were sought in which such enol formation could not occur. In dimethoxyethane, for example--a suprisingly good NC solvent--initial experiments similar to those of Table I did indeed yield incorporation of tritiated acetic anhydride into NC. At present, therefore, this appears to be the system of choice for the NC labeling.

2. MECHANICAL BEHAVIOR

a. Propellant for Macroscopic Studies

- To provide the requisite background data, mechanical property behavior will be measured upon base grain propellant and slurry cast propellant, the latter with various types of NC. This comparison will be made in two formulations, identical except for the use of a "good" plasticizer in one and a "bad" plasticizer in the other. Details of composition and testing were presented in the previous report (Ref. 3).

The casting powder and the base grain propellant are being prepared by the Naval Ordnance Station (NOS). Casting powder containing 5.1 percent TMETN and 0.6 percent TEGDN has been successfully prepared. However, some difficulties have been encountered by NOS in obtaining good propellant grains from that powder with the desired casting solvent compositions. With the approximately 1/1 TMETN/TEGDN casting solvent, for example, unexpectedly large swelling occurred, necessitating the application of significant pressures during cure; this in turn eliminated the propellant containers submitted by LPC and necessitated the use instead of NOS hardware. With the 9/1 TMETN/TEGDN casting solvent, however, insufficient swelling of the powder occurred to yield a cohesive grain, and it was therefore agreed to substitute a 4/1 TMETN/TEGDN casting solvent. (It is perhaps noteworthy that slurry cast processing of these formulations presents no serious problems.)

- As a consequence of the above, the shipment of propellant, PNC, and HMX from NOS has been delayed and this in turn has caused postponement of slurry cast propellant preparation at LPC.
- As part of the slurry cast physical property comparison, Olin has prepared ten pounds of a ball powder impregnated with approximately 10 percent of a 9/1 TMETN/TEGDN mixture. Five pounds of this impregnated powder were further enzyme-treated by Olin, a process discovered by them to be effective in removing skins. Both these powders have now been received by LPC and will be used in both the "good" and "poor" plasticizer propellant formulations.

b. Low Temperature Transitions

- Low temperature transition measurements in NC gels and propellants have been initiated, using the Differential Scanning Calorimeter (DSC).

Gel samples were prepared by adding hand-mixed plasticizer/PNC to the DSC sample pans and curing at 60°C. Samples were cooled to -100°C at approximately 5 to 10°C per minute and then scanned upwards at 40°C/minute, using an empty pan as the reference.

Initial results are shown in Figures 1 and 2 for TEGDN/NC and TMETN/NC respectively. The relatively abrupt changes seen in heat capacity are typical of glass transitions. No other transitions were observed between -100°C and +25°C. Although several studies of glass transitions in NC gels have been reported, (Ref. 4), no data are available for these particular systems for direct comparison. Taken literally, these results lead to the surprising conclusion that it is the plasticizer instead of the NC which possesses the glass transition in this region and thereby limits the low temperature physical capability. Obviously, further experimentation is needed. In particular, it will be of interest to determine whether cooling rates more pertinent for bulk samples will actually yield glass formation in the plasticizers and gels.

c. Microscope-Strain Apparatus

In order to observe the failure process in binders (intermicellar?) and propellants (dewetting?) an apparatus has been constructed which will permit microscopic observations upon thin films while the films are being strained. The apparatus is illustrated in Figures 3 and 4 and consists of a movable stage, Teflon baseplate with sample grips and attached pulley for stress application, plus a metal thermostat chamber. Thus, semi-quantitative values of stress/strain will be obtained as a function of temperature, with simultaneous visual observation, and/or photographic recording.

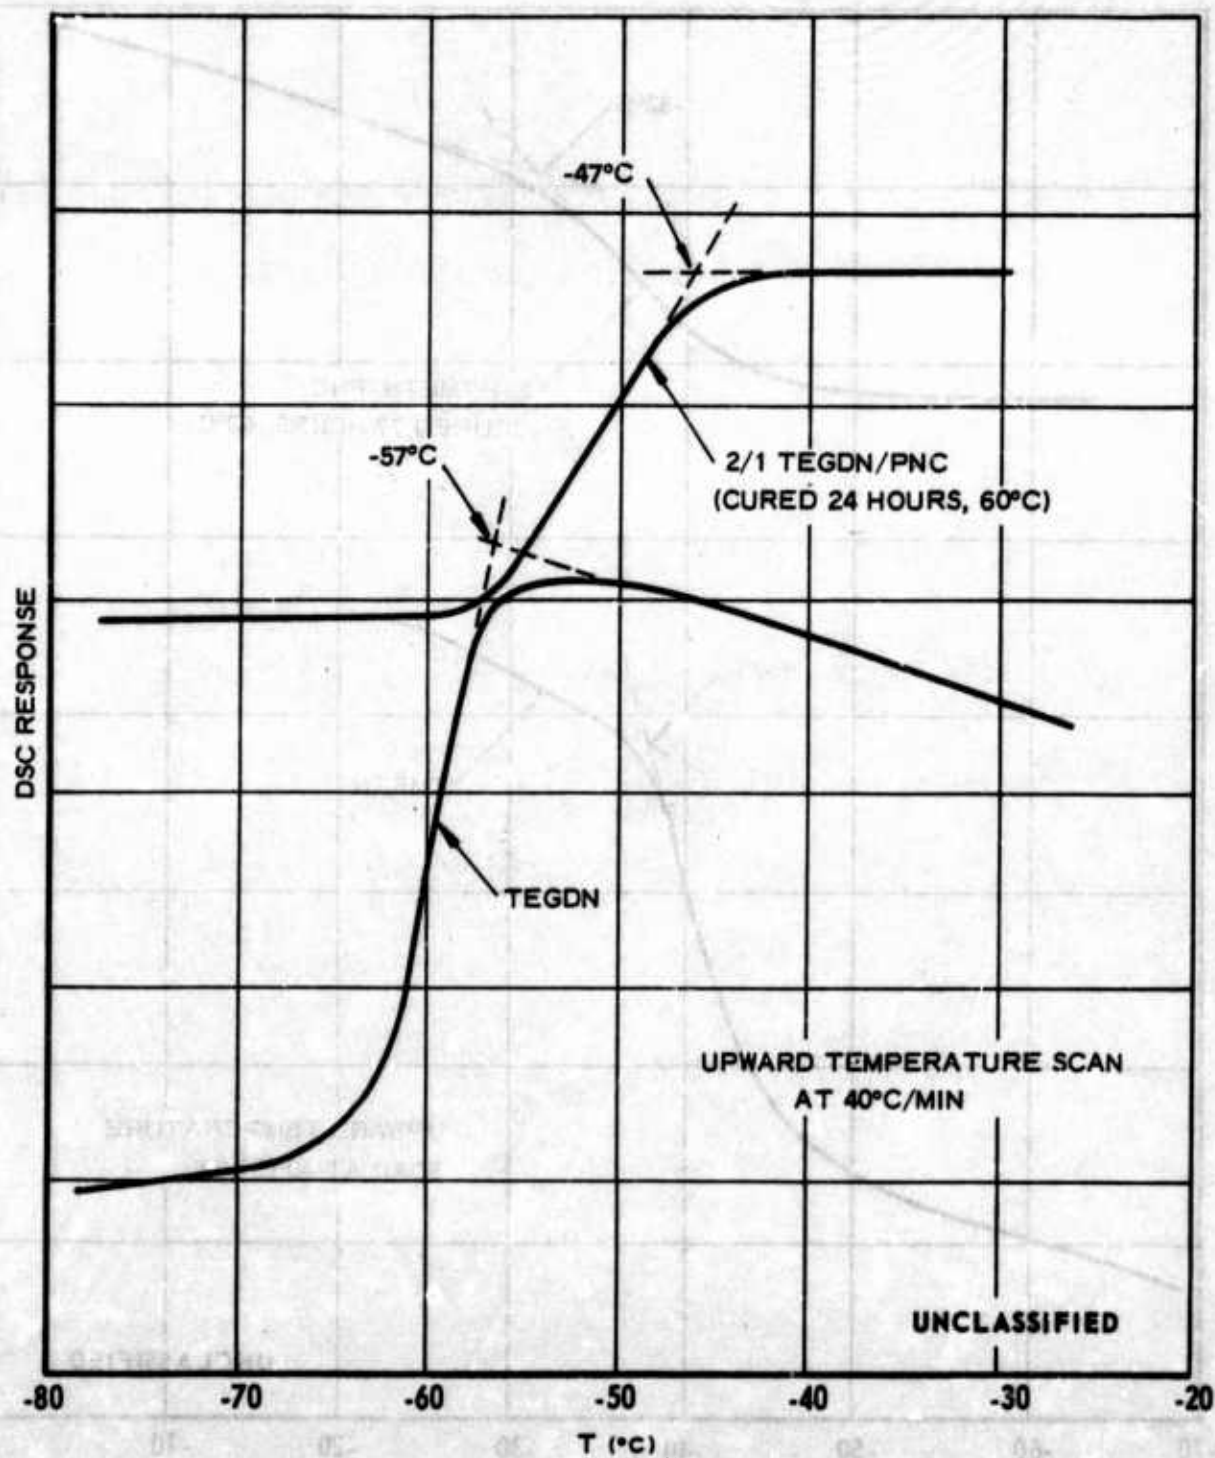


Figure 1 Glass Transition by DSC for TEGDN-NC

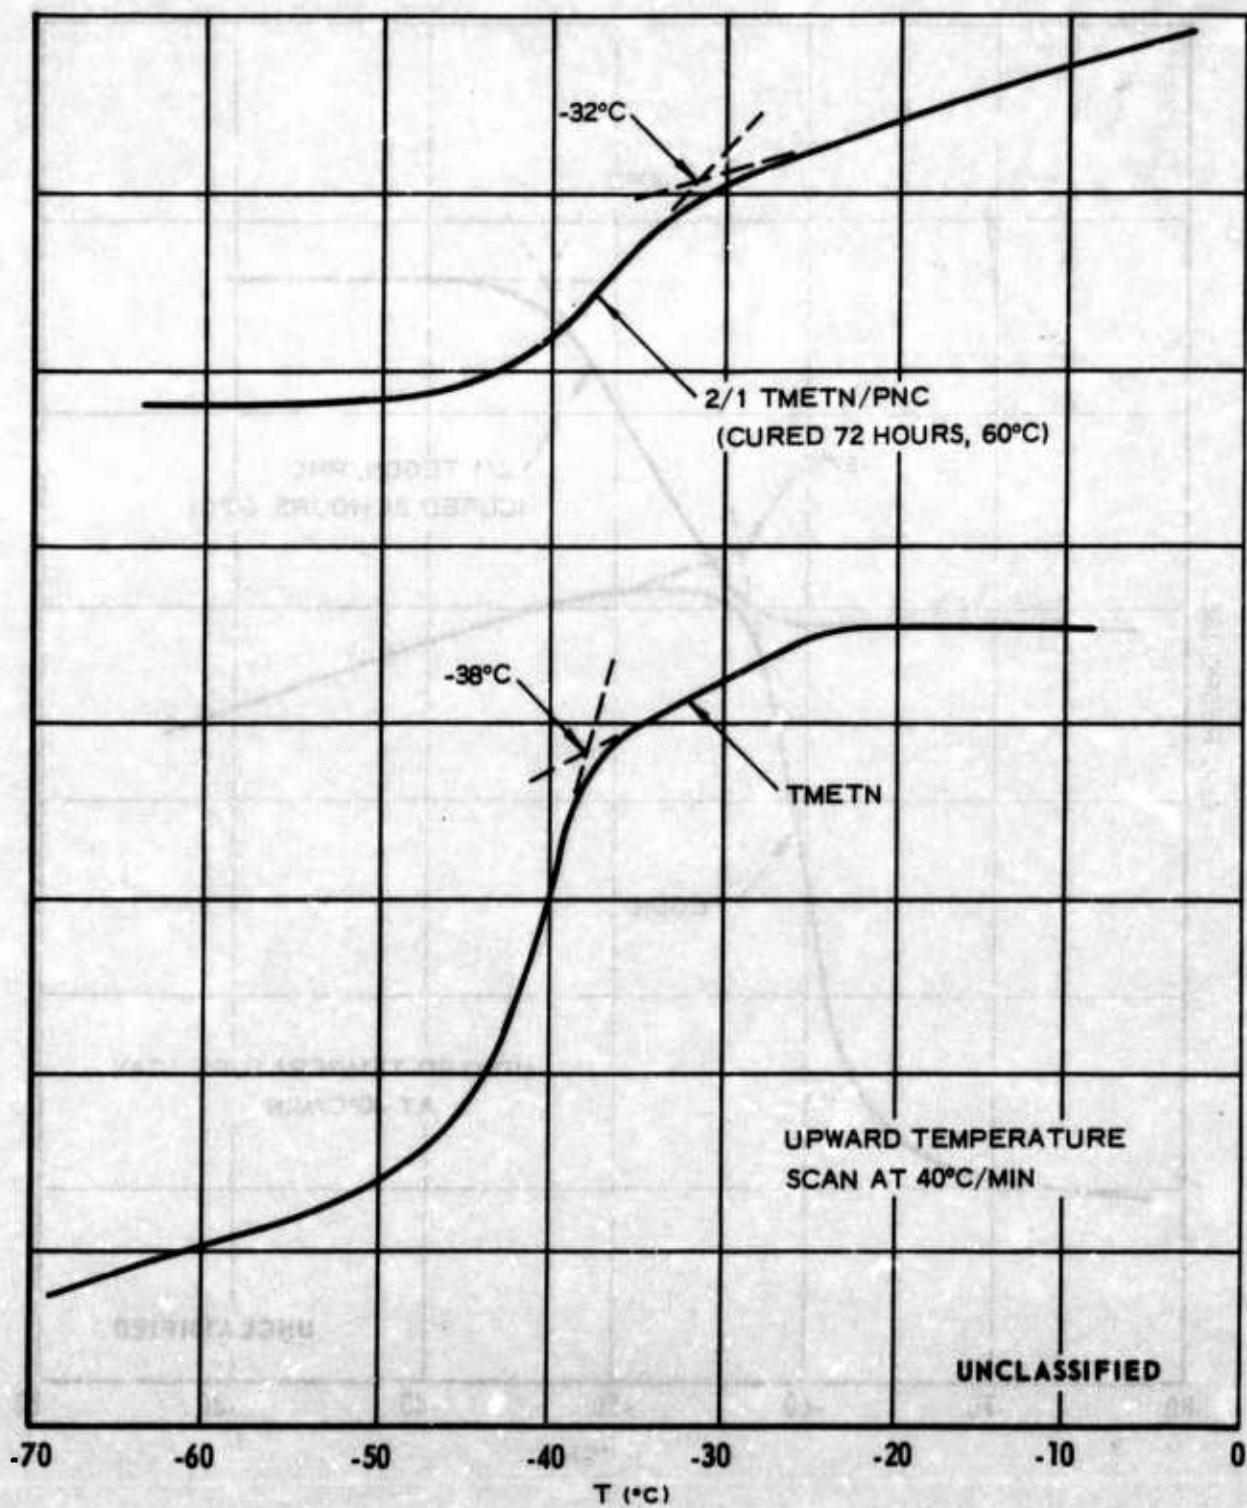


Figure 2 Glass Transition by DSC for TMETN-NC

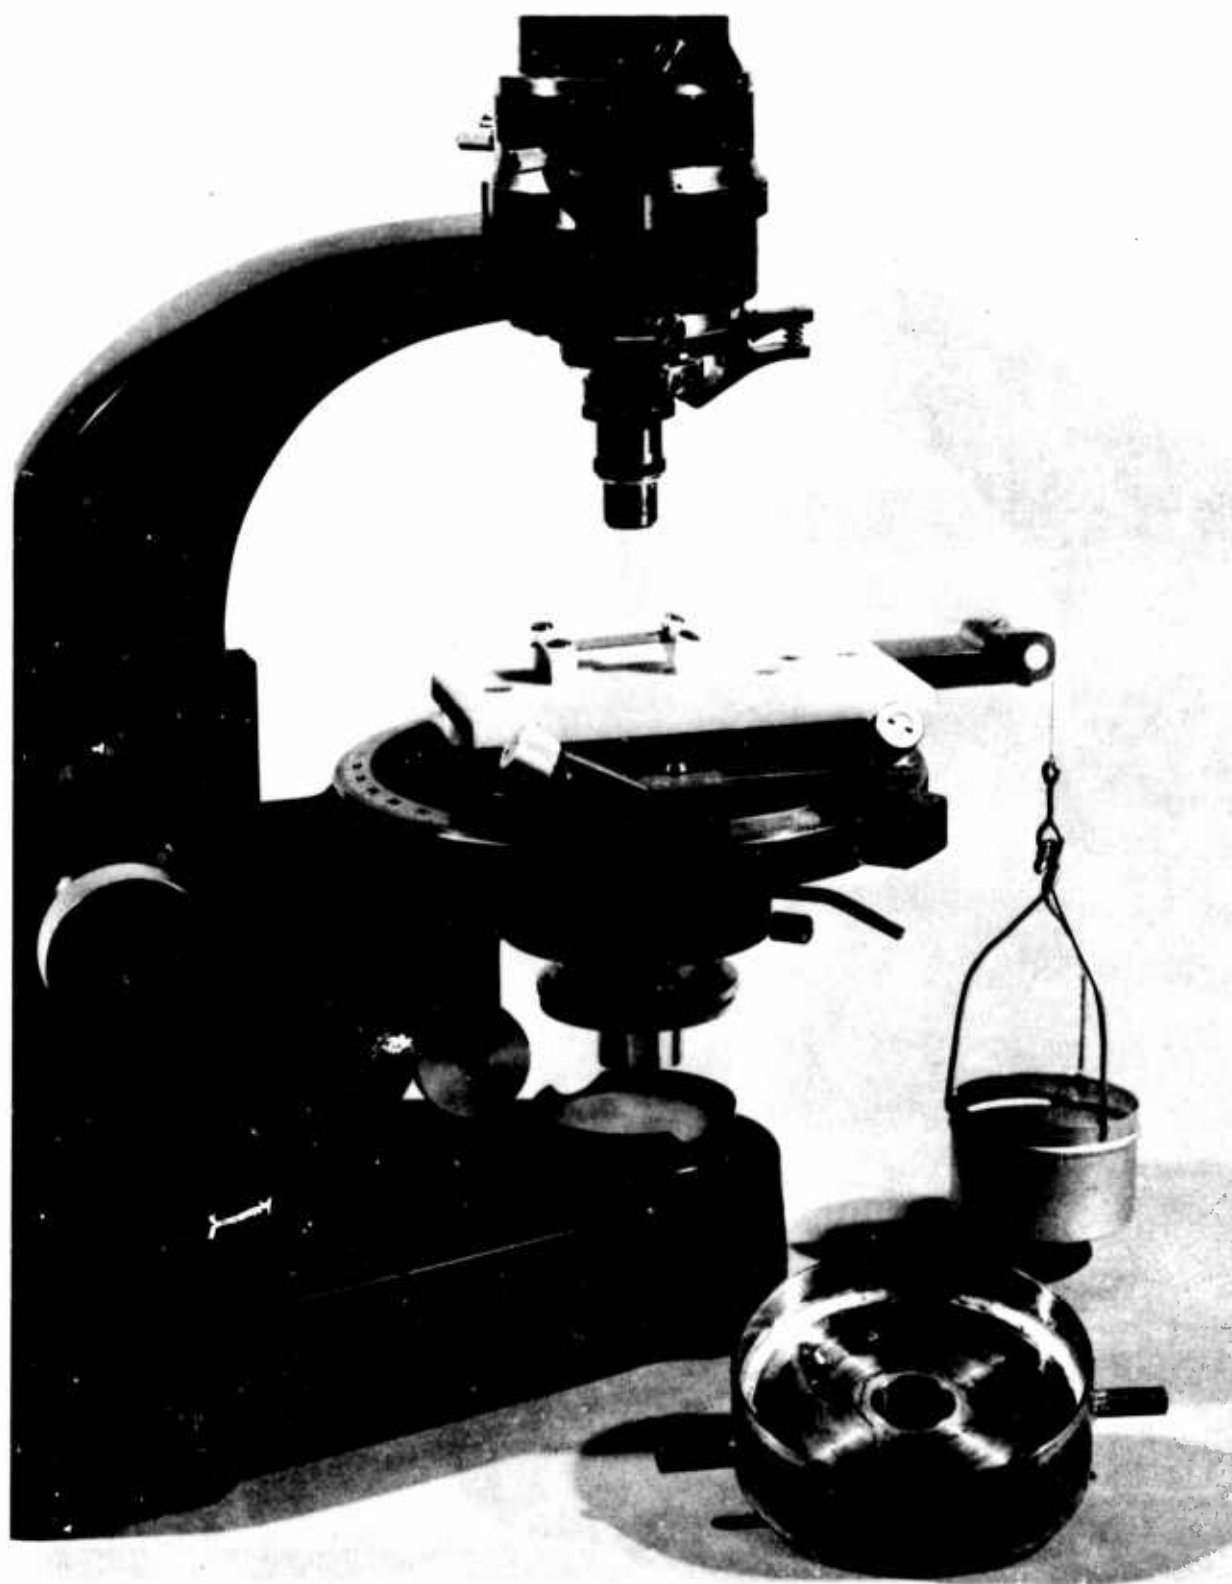


Figure 3 Microscope-Strain Apparatus, Disassembled



Figure 4 Microscope-Strain Apparatus

3. FUTURE WORK

- Experiments are continuing in tritium autoradiography. Emphasis now will be upon the examination of sections cut from bulk specimens (5 to 10 g mixes).
- Efforts toward synthesis of labeled ingredients are being held at a low level pending the degree of success obtained in the autoradiographic studies. Positive results in the latter will be followed by a resumption of NC labeling experiments and by synthesis of tritiated crosslinker (polyester caprolactone) and catalyst. The labeled NC will be incorporated by NOS into PNC and casting powder.
- Mechanical and physical property data will be obtained upon base grain and slurry cast propellants containing "good" and "bad" plasticizer compositions. These will be correlated with observed (autoradiographic, microscopic) propellant and binder structures and inhomogeneities and with NC structure and type.
- The study of low temperature transitions in binder/propellant will continue, covering the variables of composition and NC and plasticizer structure. Where desirable, these data will be supplemented by determinations of viscoelastic behavior using a micro-shear device at varying frequency and temperature (Ref. 5).
- Upon completion of a detailed review of recent literature, which is now in process, that phase of the program dealing with binder/propellant crosslinking will be initiated.

GLOSSARY

DSC	Differential Scanning Calorimeter
EGDN	Ethylene glycol dinitrate
NC	Nitrocellulose
PNC	Plastisol nitrocellulose
TEGDN	Triethylene glycol dinitrate
TME	Trimethylolethane
TMETN	Trimethylolethane trinitrate

REFERENCES

1. Laemmle, G. J., et al, Industrial and Engineering Chemistry, 52, 33 (1960).
2. Carrignan, Y. P. and J. Bobinski, Picatinny Arsenal Report No. PA TR-3105, June 1964.
3. Lockheed Propulsion Company Report No. 829-Q-1; AFRPL-TR-67-184, June 1967.
4. (a) M. A. Millett and R. C. Weatherwax, Department of Agriculture, FR October 1961.
(b) J. M. Nielsen and F. M. Ernsberger, Naval Ordnance Testing Station 708, May 1953.
5. (a) D. O. Miles, Journal of Applied Physics, 33, 1422 (1962)
(b) Lockheed Propulsion Company Report No. 667-F, AFRPL-TR-65-171 November 1965.

Unclassified
Security Classification

DOCUMENT CONTROL DATA - R&D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1. ORIGINATING ACTIVITY (Corporate author) Lockheed Propulsion Company P.O. Box 111 Redlands, California 92374		2a. REPORT SECURITY CLASSIFICATION Unclassified
		2b. GROUP
3. REPORT TITLE DOUBLE-BASE BINDER IMPROVEMENT		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Second Quarterly Technical Report covering period 1 June through 31 August 1967		
5. AUTHOR(S) (Last name, first name, initial)		
6. REPORT DATE September 1967	7a. TOTAL NO. OF PAGES 21	7b. NO. OF REFS 5
8a. CONTRACT OR GRANT NO. F04611-67-C-0078	9a. ORIGINATOR'S REPORT NUMBER(S) LPC Report No. 829-Q-2	
b. PROJECT NO. 3148		
c. BPSN 623148	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
d.	AFRPL-TR-67-254	
10. AVAILABILITY/LIMITATION NOTICES		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY Air Force Rocket Propulsion Laboratory Research and Technology Division Air Force Systems Command	
13. ABSTRACT United States Air Force, Edwards, Calif. An investigation is underway into the physio-chemical factors controlling the mechanical behavior of slurry cast and base grain composite double-base propellants, the primary objective being to improve the mechanical properties of slurry cast systems at least up to those of analogous lease grain systems. Studies during the second quarter involved establishment and testing of tritium autoradiographic procedures for investigating inhomogeneities in these systems; synthesis of tritiated ingredients; preparation of casting powder and base grain propellant by NOS and of special ball powders by Olin; observations of glass transitions in NC gels and plasticizers; construction of microscope-strain apparatus.		

DD FORM 1473
1 JAN 64

Unclassified
Security Classification

14	KEY WORDS	LINK A		LINK B		LINK C	
		ROLE	WT	ROLE	WT	ROLE	WT
<p>Double-base propellants</p> <p>Slurry cast and base grain systems</p> <p>Plasticizers</p>							

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (corporate author) issuing the report.
- 2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.
- 2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.
3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parentheses immediately following the title.
4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.
5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.
6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.
- 7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.
- 7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.
- 8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.
- 8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.
- 9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.
- 9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).
10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (paying for) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.